

MULTI-SCALE MODELING OF GLASS FIBER REINFORCED CONCRETE

Rostislav Rypl^{*}, John E. Bolander[†], Jingu Kang[†], Miroslav Vořechovský^{††}

^{*}Czech Technical University in Prague
Thákurova 7/2077, 16629 Prague 6, Czech Rep.
rypl.r@fce.vutbr.cz

[†]University of California, Davis
3121 Ghausi Hall, One Shields Avenue, Davis, CA 95616
jebolander@ucdavis.edu

^{††}Brno University of Technology
Veveří 331/95, 60200 Brno, Czech Rep.
vorechovsky.m@fce.vutbr.cz

Keywords: GFRC, Cement-based composites, Multi-scale modeling, Statistics and probability, Discrete model.

Summary: *This paper introduces and compares two approaches to simulating the crack bridging effects of chopped glass strands in cement-based matrices: a semi-analytical probabilistic model and a discrete rigid body spring network model with semi-discrete representation of the chopped strands. The strands exhibit random features at various scales. Fiber strength and interface stress are considered as random variables at the scale of a single fiber bundle while the orientation and position of individual bundles with respect to a crack plane are considered as random variables at the crack bridge scale. At the scale of the whole composite domain, the distribution of fibers and the resulting number of crack-bridging fibers is considered. All these effects contribute to the variability of the crack bridge performance and result in size-dependent behavior of the composite.*

1. INTRODUCTION

Glass fibers as reinforcement in cement-based matrix were first utilized in the 1960s in Russia [1]. A further major step towards glass fiber reinforced concrete (GFRC or GRC) was the development of alkali-resistant (AR) glass which was achieved by increasing the content (>16%) of zirconia [2, 3]. This enhancement allowed for the production of a durable high-performance cement-based composite, which has been used in various modifications in structural and military engineering since [4, 5].

Each of the AR-glass fibers is essentially a bundle of monofilaments (typically 50 to 400) which are bonded together by a sizing material. When bridging a crack, these filaments debond

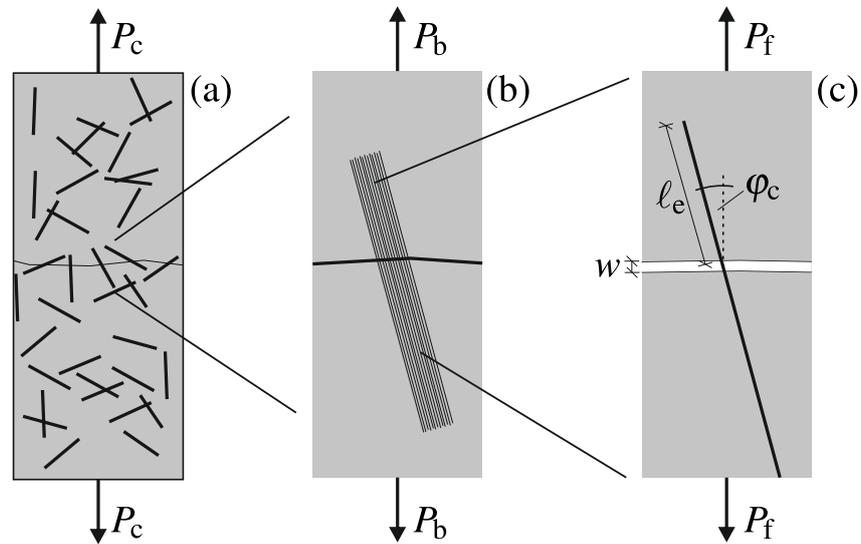


Figure 1. Multiscale approach to the modeling of GFRC: (a) composite crack bridge with multiple filament bundles; (b) filament bundle; (c) single filament considered independently from the bundle.

and rupture or are being pulled out and thus increase the toughness of the cement-based composite [6]. Moreover, the short dispersed fibers increase the first cracking stress and, above a critical volume fraction threshold, the ultimate tensile strength. These features together with the enhanced durability make the use of GFRC an alternative to traditional steel fiber reinforced concrete (FRC). However, the bridging mechanism is far more complex than in FRC.

Once a crack forms in the matrix, the glass fibers bridging the crack act against further crack opening by stretching and pullout. During this process, some filaments are completely pulled out while others rupture. The mechanism exhibits random features that can be divided into three scales:

- 1) At the micro scale, individual filaments within a bundle experience random interface shear flow depending on their position within the bundle and thus on the penetration of the matrix into the bundle core. A second source of randomness at the micro scale is the fiber strength that is determined by the weakest flaw in the material structure.
- 2) At the meso scale, individual bridging fibers are randomly oriented and positioned within the composite domain. This randomness causes variability in the bridging force due to snubbing and non-uniform pullout lengths [7]
- 3) At the macro scale, the overall number of fibers bridging a crack is a random variable that depends on the specimen geometry, fiber geometry and fiber volume fraction.

A model that considers these sources of random effects and reflects the complexity and unique bridging mechanism of the short glass fiber bundles does not exist to date.

The objective of this paper is to introduce two approaches to modeling of a crack bridge in GFRC: In Sec. 2, a probabilistic approach that predicts statistical moments of the bridging force is described. In Sec. 3, a discrete model with semi-discrete representation of the fiber bundles is presented. Both models are compared and their possibilities and limitations are discussed in Sec. 5.

2. PROBABILISTIC MODEL

The semi-analytical probabilistic model is limited to uniaxial tensile loading of a composite with discrete, planar matrix cracks and mechanically independent fibers. The mechanical independence of fibers is provided if matrix deformations are much lower than the fiber deformations i.e. the matrix stiffness $E_m(1 - V_f) \ll E_f V_f$ is much higher than that of the fibers. Here, E_m and E_f are the matrix and fiber elastic moduli, respectively, and V_f is the fiber volume fraction.

2.1 Single filament

Let us assume that the bridging action of a single filament with embedded length ℓ_e and inclination angle φ_c (with respect to the crack plane normal) is provided in the form

$$P_f = f(w, \ell_e, \varphi_c, \boldsymbol{\theta}_r, \boldsymbol{\theta}_d), \quad (1)$$

where P_f is the bridging force, w is the crack opening, $\boldsymbol{\theta}_d$ is a vector of deterministic parameters and $\boldsymbol{\theta}_r$ a vector of random variables defined over the sampling space Ω_r with the corresponding joint distribution function G_{Ω_r} . The mean force transmitted by a filament within a bundle bridging a matrix crack is

$$\mu_{P_f}(w, \ell_e, \varphi_c) = E_{\Omega_r}[P_f] \quad (2)$$

with $E_{\Omega}[\mathbf{X}]$ being the expectation operator applied to the random variable \mathbf{X} defined over the sampling space Ω with the joint probability distribution function $G_{\Omega}(\mathbf{X})$, i.e.

$$E_{\Omega}[\mathbf{X}] = \int_{\Omega} \mathbf{X} dG_{\Omega}(\mathbf{X}). \quad (3)$$

The variance of the filament bridging force is given by

$$\sigma_{P_f}^2(w, \ell_e, \varphi_c) = D_{\Omega_r}[P_f], \quad (4)$$

with $D_{\Omega}[\mathbf{X}]$ being the variance operator applied to the random variable \mathbf{X} defined over the sampling space Ω with the joint probability distribution function $G_{\Omega}(\mathbf{X})$, i.e.

$$D_{\Omega}[\mathbf{X}] = E_{\Omega}[\mathbf{X}^2] - E_{\Omega}[\mathbf{X}]^2 = \int_{\Omega} \mathbf{X}^2 dG_{\Omega}(\mathbf{X}) - E_{\Omega}[\mathbf{X}]^2. \quad (5)$$

2.2 Filament bundle

Given the number of filaments in a bundle, N_f , the force transmitted by the whole bundle reads

$$P_b = \sum_{i=1}^{N_f} P_f(w, \ell_e, \varphi_c, \boldsymbol{\theta}_{r,i}, \boldsymbol{\theta}_d), \quad (6)$$

where $\boldsymbol{\theta}_{r,i}$ is the vector of parameters obtained as the i^{th} sample from the sampling space Ω_r of the random variables $\boldsymbol{\theta}_r$. Since the inclinations and embedded lengths of the bridging bundles will be random, the φ_c and ℓ_e parameters are to be treated as random variables. Their sampling space will be referred to as Ω_φ . The mean bridging force transmitted by a bundle has the form

$$\mu_{P_b}(w) = E_{\Omega_\varphi \Omega_r}[P_b] = N_f E_{\Omega_\varphi \Omega_r}[P_f]. \quad (7)$$

For the variance of the bundle bridging force, we have to use the law of total variance, which states

$$D[Y] = E[D(Y|X)] + D[E(Y|X)]. \quad (8)$$

When this law is applied to the present case, $(Y|X)$ is substituted by $P_b(w, \ell_e, \varphi_c, \boldsymbol{\theta}_d | \boldsymbol{\theta}_r)$. We can alternatively express the conditional probability by explicitly writing the integration domain for individual statistical operators in the equation. With this notation, the variability of the randomly oriented filament bundle with random embedded length reads:

$$\begin{aligned} \sigma_{P_b}^2(w) &= E_{\Omega_\phi} [D_{\Omega_r}(P_b)] + D_{\Omega_\phi} [E_{\Omega_r}(P_b)] \\ &= N_f^2 (E_{\Omega_\phi} [D_{\Omega_r}(P_f)] + D_{\Omega_\phi} [E_{\Omega_r}(P_f)]). \end{aligned} \quad (9)$$

where do not explicitly write out the dependencies of P_f on its parameters.

2.3 Multiple bundles

Let us now introduce the variable N_b , which stands for the number of bundles (chopped strands) bridging a matrix crack. In a composite with randomly dispersed fiber bundles, N_b will be a random variable with sampling space Ω_b . The total force transmitted by all N_b bundles can be written as

$$P_c = \sum_{j=1}^{N_b} \sum_{i=1}^{N_f} P_f(w, \ell_{e,j}, \varphi_{c,j}, \boldsymbol{\theta}_{r,ij}, \boldsymbol{\theta}_d) = \sum_{j=1}^{N_b} P_{b,j}, \quad (10)$$

where $\ell_{e,j}$ and $\varphi_{c,j}$ are the j^{th} samples from the Ω_φ sampling space, the vector $\boldsymbol{\theta}_{r,ij}$ is the ij^{th} sample from the sampling space Ω_r and $P_{b,j}$ is the obvious identity

$$P_{b,j} = \sum_{i=1}^{N_f} P_f(w, \ell_{e,j}, \varphi_{c,j}, \boldsymbol{\theta}_{r,ij}, \boldsymbol{\theta}_d). \quad (11)$$

The mean force resulting from the bridging action of randomly dispersed short fiber bundles has the form

$$\begin{aligned}\mu_{P_c}(w) &= \mathbb{E}_{\Omega_b, \Omega_\varphi, \Omega_r}[P_c] = \mathbb{E}_{\Omega_b}[N_b] \mu_{P_b}(w) \\ &= \mathbb{E}_{\Omega_b}[N_b] N_f \mathbb{E}_{\Omega_\varphi, \Omega_r}[P_f].\end{aligned}\quad (12)$$

Applying the law of total variance according to Eq. (8) with $P_c(w, \ell_e, \varphi_c, \boldsymbol{\theta}_r, \boldsymbol{\theta}_d | N_b)$ substituted for $(Y|X)$, the variance of the crack bridging force P_c is obtained as

$$\begin{aligned}\sigma_{P_c}^2(w) &= \mathbb{D}_{\Omega_b, \Omega_\varphi, \Omega_r}[P_c] = \mathbb{D}_{\Omega_b, \Omega_\varphi, \Omega_r} \left[\sum_{j=1}^{N_b} P_{b,j} \right] \\ &= \mathbb{E}_{\Omega_b} \left[\mathbb{D}_{\Omega_\varphi, \Omega_r} \left(\sum_{j=1}^{N_b} P_{b,j} \middle| N_b \right) \right] + \mathbb{D}_{\Omega_b} \left[\mathbb{E}_{\Omega_\varphi, \Omega_r} \left(\sum_{j=1}^{N_b} P_{b,j} \middle| N_b \right) \right]\end{aligned}\quad (13)$$

Exploiting the independence of $P_{b,j}$ and N_b , Eq. (13) can be simplified to

$$\begin{aligned}\sigma_{P_c}^2(w) &= \mathbb{E}_{\Omega_b} [N_b \cdot \mathbb{D}_{\Omega_\varphi, \Omega_r}(P_{b,j})] + \mathbb{D}_{\Omega_b} [N_b \cdot \mathbb{E}_{\Omega_\varphi, \Omega_r}(P_{b,j})] \\ &= \mathbb{E}_{\Omega_b}[N_b] \cdot \mathbb{D}_{\Omega_\varphi, \Omega_r}[P_{b,j}] + \mathbb{D}_{\Omega_b}[N_b] \cdot (\mathbb{E}_{\Omega_\varphi, \Omega_r}[P_{b,j}])^2.\end{aligned}\quad (14)$$

In order to evaluate the statistical moments of the bridging response, the distribution functions of the random variables need to be known. The derivation of distribution functions for individual random variables is out of the scope of the present publication so that we refer to [8] for the distribution of the strength of a brittle fiber in composite and the bond strength distribution. The distribution of the number of dispersed short fibers bridging a planar matrix crack is in detail dealt with in [9].

3. DISCRETE MODEL

The fiber and matrix phase models are both based on a lattice model. The matrix phase is represented by a set of randomly distributed nodes which are interconnected by springs and kinematic constraints. This nodal set for the matrix phase has lattice topology and material properties by the Delaunay/Voronoi tessellations which enable the discretized matrix phase to behave in an elastically homogeneous fashion (Fig. 2a). As shown Fig. 2b, the matrix element is defined according to the rigid-body-spring concept [10]. The linear and rotational zero-size springs are formed at the centroid C of the area A_{ij} of the Voronoi facet common to nodes i and j . The spring set is constrained to nodes i and j via rigid arm constraints.

The fiber phase can be discretized within the computational domain irrespective of the background lattice representing the matrix [11]. A fiber element is defined wherever a fiber passes through the Voronoi facet A_{ij} associated with a matrix element (Fig. 2c). In the semi-discrete fiber model, a linear zero-size spring for the fiber reinforcement is positioned at the intersection point I and aligned with the fiber path. The spring is linked to the associated two nodes i and j through rigid-arm constraints similar to the rigid-body-spring construction of the matrix elements. The semi-discrete modeling of fibers is computationally efficient, contrary to the

fully-discrete fiber modeling in which a fiber is discretized as a series of the frame elements with additional nodal degrees of freedom and its elements are linked to the associated nodes via an ordinary bond link. This feature of the semi-discrete fiber model enables simulations with large numbers of fibers.

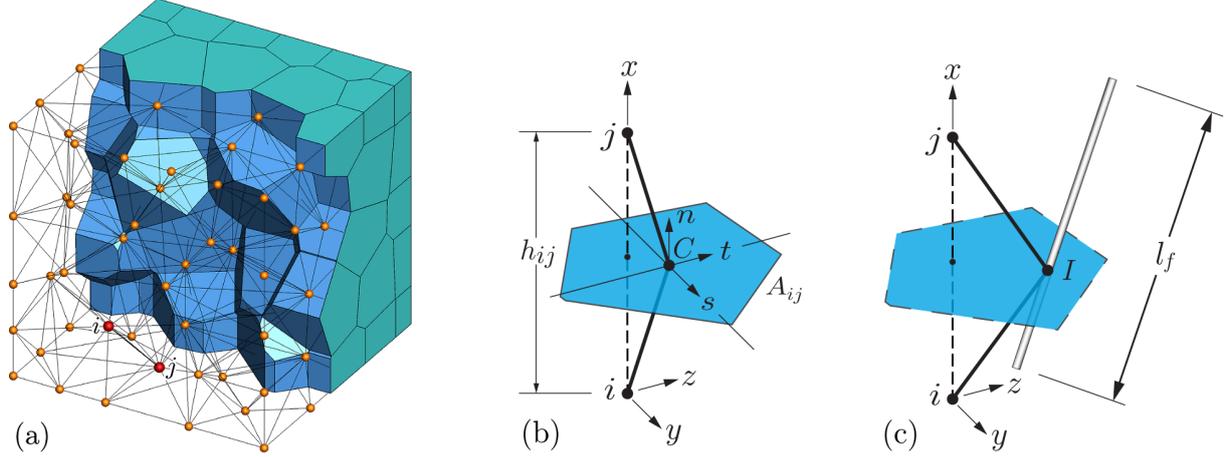


Figure 2. Lattice discretization of fiber reinforced concrete: (a) Delaunay/Voronoi tessellations of material domain; (b) matrix element ij defined by facet centroid C ; and (c) fiber element associated with intersection point I .

4. COMPUTATIONAL EXAMPLE

Having formulated the modeling framework for GFRC in two alternatives, we can proceed to a computational example, which compares the two approaches. Both models require an independent model of a fiber bridging action. For this purpose, we apply the analytical form due to [12] with snubbing and spalling effects according to [13]. For reasons of brevity and readability, we simplify the general expressions by assuming a perfectly plastic (frictional) bond with infinite initial stiffness and constant bond strength. With these assumptions, the resulting form for a filament bridging action in the debonding phase reads

$$F_{f,\text{deb}}(w, \sigma_u = \infty) = A_f \sqrt{\frac{2E_f \tau w}{r_f}} \cdot \exp(f\varphi_c) \cdot (\cos \varphi_c)^s \quad (15)$$

with E_f , A_f and r_f being the filament modulus of elasticity, cross-sectional area and radius, respectively, τ denoting the bond strength, f the snubbing coefficient and s the spalling coefficient. When the fiber is fully debonded along the embedded length ℓ_e , the pullout stage starts. Again, for reasons of brevity, we ignore any hardening or softening during the pullout stage and write the bridging force during the pullout stage simply as

$$F_{f,\text{pull}}(w, \sigma_u = \infty) = 2\pi r_f \tau (\ell_e + w_0 - w) \cdot \exp(f\varphi_c) \cdot (\cos \varphi_c)^s \quad (16)$$

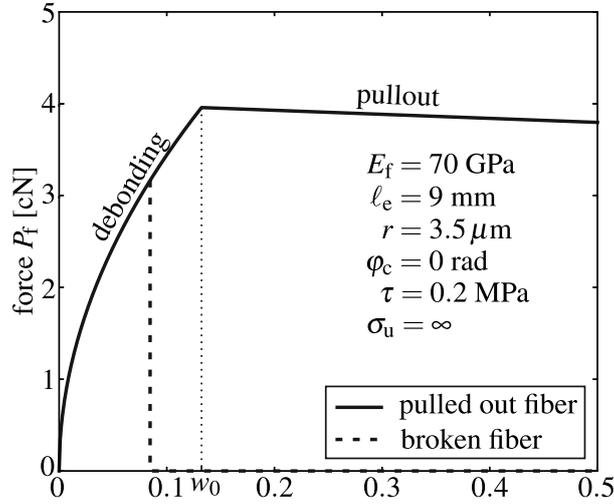


Figure 3. Analytical model of a single fiber bridging action due to Naaman et al. [12].

with w_0 being the crack opening at the transition between the debonding and pullout stage. It can be obtained by formulating the continuity condition

$$F_{f,\text{deb}}(w_0)F_{f,\text{pull}}(w_0) \rightarrow w_0 = \frac{2\ell_e^2\tau}{r_f E_f}. \quad (17)$$

In both Eq. (15) and Eq. (16), the assumption was that fibers have an infinite strength $\sigma_u = \infty$. If we now include the possibility of fiber rupture, we have to multiply the fiber force in the debonding phase by $H(\sigma_u - \sigma_f)$, where σ_f denotes the fiber stress and $H(\cdot)$ the Heaviside step function defined as

$$H(x) = \begin{cases} 0 & : x < 0 \\ 1 & : x \geq 0. \end{cases} \quad (18)$$

The filament force in the debonding stage then becomes

$$F_{f,\text{deb}}(w) = A_f \sqrt{\frac{2E_f\tau w}{r_f}} \cdot \exp(f\varphi_c) \cdot (\cos\varphi_c)^s \cdot H(\sigma_u - \sigma_f) \quad (19)$$

with

$$\sigma_f = \frac{F_{f,\text{deb}}(w, \sigma_u = \infty)}{A_f}. \quad (20)$$

In a similar manner, the pullout force has to be multiplied by a Heaviside function which ensures that fibers have not ruptured at their peak stress during the debonding so that

$$F_{f,\text{pull}}(w) = 2\pi r_f \tau (\ell_e + w_0 - w) \cdot \exp(f\varphi_c) \cdot (\cos\varphi_c)^s \cdot H(\sigma_u - \sigma_{f,\text{max}}), \quad (21)$$

where

$$\sigma_{f,\text{max}} = \frac{2\pi r_f \tau \ell_e}{A_f}. \quad (22)$$

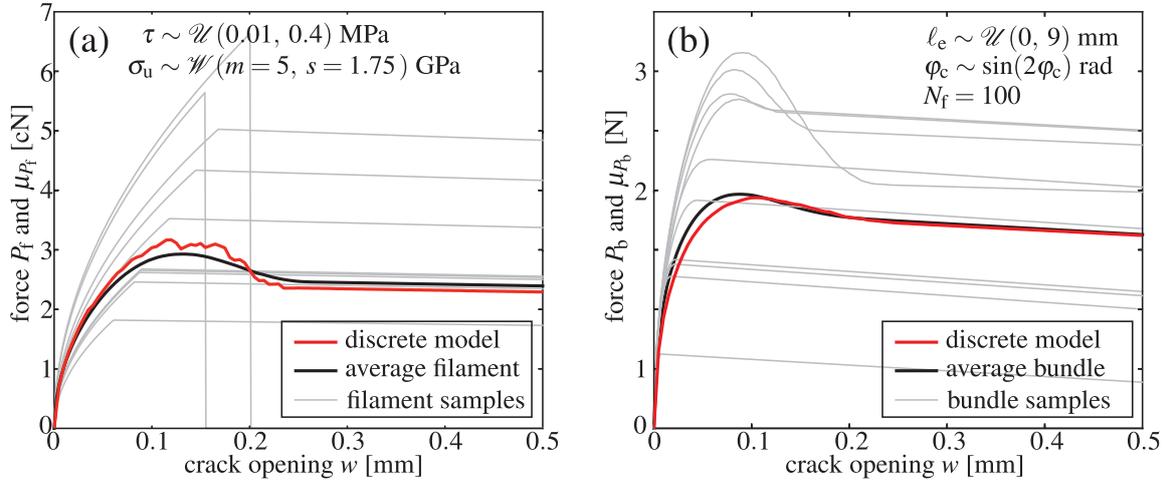


Figure 4. Computational example performed with the present modeling framework: (a) single filament bridging responses (gray curves) sampled from the sampling space of random variables ($\tau \sim$ uniform distribution between 0.01 and 0.4 MPa and $\sigma_u \sim$ Weibull distribution with shape $m = 5$ and scale $s = 1.75$ GPa) and mean filament response (black curve); (b) filament bundle responses sampled from the sampling space of random variables ($\varphi_c \sim \sin(2\varphi_c)$ rad and $l_e \sim$ uniform distribution between 0 and 9 mm) and mean bundle response (black curve).

The complete filament bridging action (see Fig. 3) can be written as

$$P_f(w) = F_{f,\text{deb}}(w) \cdot H(w_0 - w) + F_{f,\text{pull}} \cdot H(w - w_0). \quad (23)$$

An example of the filament bridging action is depicted in Fig. 4a for material parameters that correspond to AR-glass fibers with random τ distributed uniformly between 0.01 and 0.4 MPa and random fiber strength σ_u with Weibull distribution with shape parameter $k = 5$ and scale parameter $\lambda = 1.75$ GPa. The filaments are embedded perpendicular to the crack plane in this example. The figure shows samples from the distributions given by Eq. (23) and the mean filament response given by Eq. (2), which, multiplied by the number of filaments in a bundle, is the prediction of the response of a perpendicularly embedded filament bundle. The red curve is a single simulation of a bundle consisting of 100 filaments performed by the discrete model.

Fig.4b depicts the bridging force of a bundle consisting of $N_f = 100$ filaments with random bond strength and fiber strength as in Fig. 4a but, additionally, the orientation angle and embedded length are considered as random variables. Random samples of such filament bundles and the mean bundle bridging force predicted by the probabilistic model with Eq. (7) are depicted. The red curve is the bridging force of $N_b = 100$ bundles that are randomly oriented and positioned within the crack predicted by the discrete model.

5. CONCLUSIONS

Both the probabilistic and the discrete model are capable of simulating the crack bridging action of chopped AR-glass strands in a cement-based matrix. The probabilistic model is com-

putationally very efficient and able to evaluate statistical moments of the response. However, the model formulation includes a number of assumption that make the model of use only for uniaxial tension in its current form.

The discrete model evaluates the response of the composite as a single sample. Therefore, repeated calculations would have to be performed when the variability was of interest. The discrete model, even though more computationally demanding, is much more robust than the probabilistic model. It is not limited to uniaxial tension and is therefore suitable for general purposes. Its comparison with the probabilistic model serves as a verification of the semi-discrete fiber bundle implementation.

6. ACNOWLEDGMENTS

This publication was supported by the European social fund within the framework of realizing the project „Support of inter-sectoral mobility and quality enhancement of research teams at Czech Technical University in Prague“, CZ.1.07/2.3.00/30.0034. The support is gratefully acknowledged.

References

- [1] K.L Biryukovich, Y. Biryukovich, and D.L Biryukovich. *Glass fibre reinforced cement*. CERTA Translation No. 12 Civil Engineering Research Assotiation, London, 1965.
- [2] W. Wolf Warren. Glass fiber reinforced cement, 1975. US Patent 3,902,912.
- [3] A.J. Majumdar and J.F Ryder. Glass fibre reinforcement for cement products. *Glass Technology*, 9:78–84, 1968.
- [4] H. Ball. 35 year review of the grc technology, equipment and markets. In *GRCA Congress*, Istanbul, 2011.
- [5] M.J. Roth, C.D. Eamon, T.R. Slawson, T.D. Tonyan, and A. Dubey. Ultra-high-strength, glass fiber-reinforced concrete: Mechanical behavior and numerical modeling. *ACI Materials Journal*, 2:185–194, 2010.
- [6] B. Mobasher and S.P. Shah. Test parameters for evaluating toughness of glass fiber reinforced concrete panels. *Materials Journal*, 86:448–458, 1989.
- [7] V.C. Li, Y. Wang, and S. Backer. A micromechanical model of tension-softening and bridging toughening of short random fiber reinforced brittle matrix composites. *Journal of the Mechanics and Physics of Solids*, 39(5):607–625, 1991.
- [8] R. Rypl, R. Chudoba, A. Scholzen, and M. Vořechovský. Brittle matrix composites with heterogeneous reinforcement: Multi-scale model of a crack bridge with rigid matrix. *Composites Science and Technology*, 89:98–109, December 2013.

- [9] M. Vořechovský, V. Sadílek, and R. Rypl. Probabilistic evaluation of crack bridge performance in fiber reinforced composites. *Engineering mechanics*, 20(1):3–11, 2013.
- [10] J.E. Bolander and N. Sukumar. Irregular lattice model for quasistatic crack propagation. *Physical Review B*, 71:094106, 2005.
- [11] J. Kang, K. Kim, Y.M. Lim, and J.E. Bolander. Modeling of fiber-reinforced cement composites: Discrete representation of fiber pullout. *International Journal of Solids and Structures*, 51:1970–1979, 2014.
- [12] A.E. Naaman, G.G. Namur, J.M. Alwan, and H.S. Najm. Fiber pullout and bond slip. I: Analytical study. *Journal of Structural Engineering*, 117(9):2769–2790, 1991.
- [13] Y. Lee, S.T. Kang, and J.K. Kim. Pullout behavior of inclined steel fiber in an ultra-high strength cementitious matrix. *Construction and Building Materials*, 24:2030–2041, 2010.